



SYNTHESIS OF SILVER NANOPARTICLES VIA GREEN APPROACH USING FRUIT EXTRACT OF *CUPRESSUS SEMPERVIRENS* L. AND THEIR ANTIMICROBIAL EVALUATION

BHAWNA PAWAR* AND DEVENDRA SINGH NEGI

Department of Chemistry, HNB Garhwal University (A Central University), Srinagar, Garhwal-246174, Uttarakhand, India

ABSTRACT

In this study, silver nanoparticles have been synthesized using extract of *Cupressus sempervirens* fruit in aqueous solution at room temperature. The fruit extract was able to reduce Ag^+ to Ag^0 and stabilized the nanoparticles. Different physico-chemical techniques including UV-Vis spectroscopy, X-ray diffraction (XRD), scanning electron microscopy (SEM) and transmission electron microscopy (TEM) with EDX were used for the characterization of biosynthesized silver nanoparticles obtained. The surface resonance band appeared at 450 nm is an evidence for formation of AgNPs. The XRD pattern showed the characteristic Bragg peaks of (111), (200), (220) and (311) facets of the face centre cubic (fcc) silver nanoparticles and confirmed that these nanoparticles are crystalline in nature. SEM micrograph showed that the synthesized Ag-NPs have spherical shape. HRTEM analysis showed particles with an average size of 29 nm. The silver nanoparticles possess significant antimicrobial potential against *B.cereus* and *K. pneumoniae*.

KEY WORDS: *Cupressus sempervirens*, silver nanoparticles, XRD, SEM, TEM, antimicrobial activity.



BHAWNA PAWAR*

Department of Chemistry, HNB Garhwal University (A Central University),
Srinagar, Garhwal-246174, Uttarakhand, India

Received on: 30-08-2016

Revised and Accepted on: 16-03-2017

DOI: <http://dx.doi.org/10.22376/ijpbs.2017.8.2.p156-162>

INTRODUCTION

Nowadays, nanotechnology has grown to be an important research field in all areas including medicinal chemistry¹. Nanotechnology deals with the nanoparticles having a size of 1-100 nm. The nano particles exhibit completely new or improved properties based on specific characteristics such as size, distribution and morphology^{2,3}. Particles of this size scale (1-100 nm) show different and novel chemical, physical and biological properties and activities in comparison to the bulk materials⁴. Metallic nanoparticles are one of the most promising antibacterial nanomaterials⁵. Silver is efficient antimicrobial agent compared to other salts due to their extremely large surface area, which provides better contact with microorganism⁶. Silver nanoparticles (Ag-NPs) are proved to have high potential antimicrobial, antiplasmodial, and antifungal properties, so recently, they have been used for controlling harmful microorganismssuch as bacteria, molds, yeasts and viruses^{7,8}. Different routes have been developed to synthesize Ag-NPs while striving to consume less energy, increase efficiency and more importantly to develop ecofriendly procedures^{9,10,11,12}. One of such methods is the production of Ag-NPs using biological systems, such as bacteria^{9,13}, fungi¹⁴, algae^{15,16} and plants^{17,18}. The use of plant extractor plant biomass for the production of nanoparticles could be an alternative to chemical and physical methods in an eco-friendly manner¹⁹. Plants extracts/products having a wide range of metabolites, silver nanoparticles produced by plant extracts are more stable and rate of synthesis is faster in comparison to microorganism. Metabolites and other constituents as reducing agents present in the plants acts as stabilizing and capping agents, so there is no need of adding capping and stabilizing agents from outside²⁰. *Cupressus sempervirens*, the Mediterranean cypress (also known as Italian cypress) belongs to *Cupressaceae* family. It was native to the Mediterranean basin. However, it is distributed in North America and subtropical Asia at high altitude. *C. sempervirens* L. were reported to have antiseptic, aromatherapeutic, astringent, balsamic, and anti-inflammatory activities²¹. Its dried fruits are used for the inflammation treatment, toothache, and laryngitis and also as a contraceptive as well asastringent. *Cupressus sempervirens* L. revealed that it contains active constituents such as flavonoids (rutin, quercetin, and myricitrin), phenolic compounds (anthocyanidin, flavones, flavonols and tannins), and essential oils. The present study reports green synthesis of Ag-NPs using fruit extract of *C. sempervirens* and to evaluate antimicrobial properties of synthesized Ag-NPs. To the best of our knowledge, this study is the first time report of Ag-NPs synthesis using aqueous fruit extract of *C. sempervirens*.

MATERIALS AND METHODS

Materials

All analytical reagents and media components were purchased from Merck Chemicals. The deionized water was used throughout the experiment. All glassware's

were properly washed with distilled water and oven dried before use. Fresh fruit of *C. sempervirens* were collected from Almora, Uttarakhand and identified by Botany Division, Central Drug Research Institute, Lucknow. The voucher specimen (No.24421) is stored in the herbarium of the institute.

Preparation of Plant extract

Prior to the experiment, *C. sempervirens* fruit was rinsed thoroughly by deionized water. The plant material shade dried at room temperature. The dried plant material was powdered and 10 g of powder mixed with 100 mL of deionized water in a 250 mL Erlenmeyer flask and mixture was boiled for 15 min. The solution was cooled at room temperature and filtered by Whatman filter paper No. 1. The filtrate was collected and stored at 4°C for further experiment.

Preparation of silver nanoparticles

Silver nanoparticles were synthesized by reducing the freshly prepared 3 mM silver nitrate (AgNO₃) and stored under dark conditions with aqueous extract of the plant. The reaction mixture was prepared in ratio of 9:1 (V/V) comprised of freshly prepared silver nitrate solution and plant extract respectively. After 15 min the color change of the solution from pale yellow to dark brown was observed. The solution was stored at room temperature for the complete settlement of nanoparticles. After 24 hours the reaction mixture was centrifuged at 4000 rpm for 20 min and pellets were collected followed by washing with deionized water and dried in water glass.

UV-VIS spectra analysis

The UV-Visible spectrum of synthesized silver nanoparticles was analysed by spectrophotometer (UV-Visible Perkin Elmer Lambda 25). Absorption wavelength was studied range between 200 and 800 nm. The silver nanoparticles show the surface Plasmon resonance at 400 to 500 nm in the UV-Visible spectrum.

XRD analysis of silver Nanoparticles

The particle size and nature of the Ag-NPs were determined with X-ray diffraction using Smartlab (Rigaku), operating at 40 kV, 40 mA with Cu K α radiation at 2 θ angle ranging from 20° to 80°. The crystallite size of the silver nanoparticles was estimated using Debye Sherrer's equation. $D = 0.94 \lambda / \beta \cos \theta$ where D is the average crystallite size, λ is the wavelength of X-ray source (0.15406 nm), β is the full width at half maximum (FWHM), and θ is the diffraction angle.

SEM analysis of silver nanoparticles

To observe the morphology of the synthesized Ag-NPs, images were obtained by a FESEM (Sigma, Carl Zeiss) instrument. Thin films of the sample were prepared on a gold coated copper grid by just dropping a very small amount of the sample on the grid. The details regarding applied voltage, magnification used and size of the contents of the images were implanted on the images itself.

TEM analysis of silver nanoparticles

The particle size shape and surface morphology was confirmed using Transmission electron microscopy

(TEM). High Resolution Transmission Electron Microscopy (HRTEM) was performed by Tecnai G2 F30 S-Twin(FEI) machine, operated at an accelerated voltage of 300 kV. These images were taken by drop coating Ag-NPs on a carbon-coated copper grid. Additionally, addition presence of metals in the sample was analysed by Energy Dispersive Spectroscopy (EDS). EDS photograph of Ag-NPs were carried out by the HRTEM instrument equipped with EDX detector as mentioned above.

Antibacterial Property of Ag-NPs

The antibacterial activity of the silver nanoparticles was determined against the human pathogenic bacteria *viz.* *Bacillus cereus* and *Klebsiella pneumoniae* by disk diffusion method using a Mueller-Hinton agar culture medium (Hi-media). The standard cultures were inoculated 10^8 CFU/ml in petri dishes with MH agar medium and then paper disks of 5mm diameter were laid on the inoculated standard culture, which was instilled with nanoparticles neat solution in DMSO. Petri dishes were incubated at 37°C for 24 hrs. and antimicrobial activity was determined by measuring the

zone of inhibition around the disk. The test was done in triplicate.

RESULTS AND DISCUSSION

UV-Vis spectra Analysis

The silver nanoparticles were characterized by UV-Vis spectroscopy, one of the most widely used techniques for structural characterization of silver nanoparticles. Silver nanoparticles (AgNPs) appear pale yellowish to dark brown in colour in aqueous medium as a result of surface Plasmon vibrations²². The green synthesis of silver nanoparticles using *C. sempervirens* extract was successfully carried out. The UV-vis spectra recorded after time intervals of 15 min, 30 min, 60 min and 24 h from the initiation of reaction are shown in Figure 1. Absorption spectra of Ag-NPs formed in the reaction media has absorption maxima in the range of 441 to 450 nm due to surface Plasmon resonance of Ag-NPs. In the spectrum, broadening of peak indicated that the particles are polydispersed.

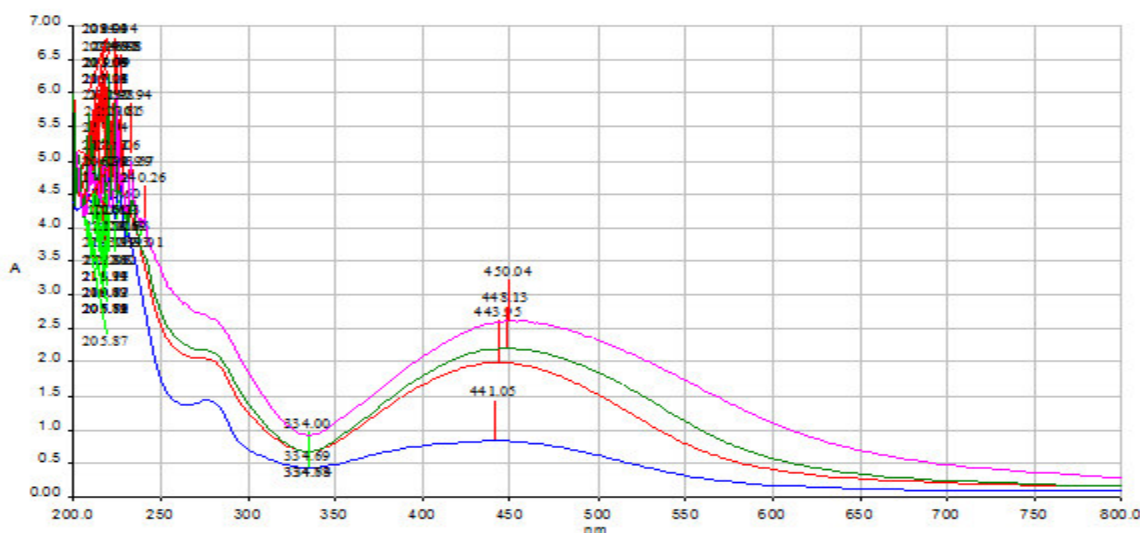


Figure 1
UV-Vis absorption spectra of Ag-NPs

XRD analysis

The XRD pattern of synthesized silver nanoparticles using *C. sempervirens* extract were recorded and XRD pattern is shown in Figure 2. The XRD pattern confirms the crystalline structure of the Ag-NPs. In the spectrum, peaks observed at 38.17° , 44.26° , 64.54° and 77.41° are

corresponded to (111), (200), (220) and (311) planes of pure face centered crystalline (fcc) structure of silver. Crystallite size of Ag-NPs as estimated from the FWHM of different peaks using the Scherrer's formula and diffraction lines observed at 2θ angle are given below (Table.1).

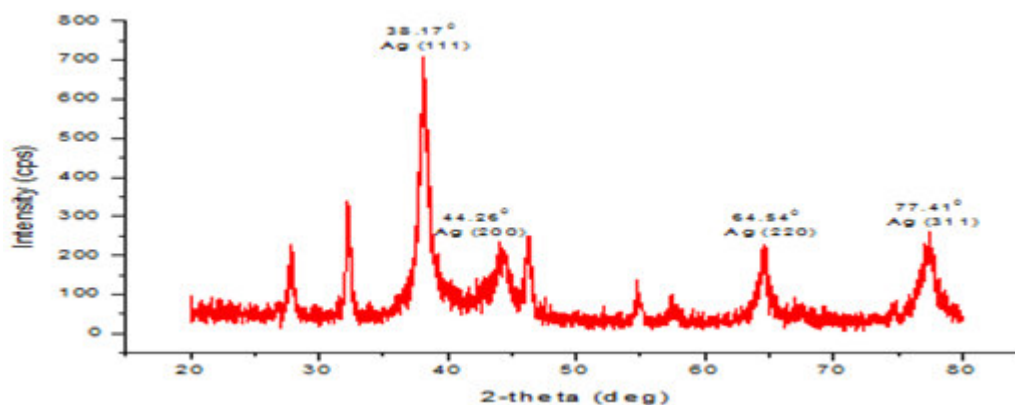


Figure 2
XRD pattern of silver nanoparticles of *C. sempervirens*

Table 1
Crystalline size of Ag-NPs synthesized using *C. sempervirens*

| No. | 2-Theta (deg) | D (ang) | FWHM (deg) | Plane | Average size Nm |
|-----|--------------------|---------|------------|-------|-----------------|
| 1. | 38.17 ⁰ | 2.3540 | 0.79 | 100 | 11.1 |
| 2. | 44.26 ⁰ | 2.045 | 1.71 | 200 | 5.2 |
| 3. | 64.54 ⁰ | 1.4395 | 0.74 | 220 | 13.2 |
| 4. | 77.41 ⁰ | 1.2291 | 1.30 | 311 | 8.2 |

SEM analysis

The SEM micrograph showing the high density Ag-NPs synthesized by the *C.sempervirens* further confirmed the development of silver nanoparticles. The SEM

micrographs of nanoparticles showed that Ag-NPs are spherical shaped, well distributed without aggregation in solution. (Figure 3)

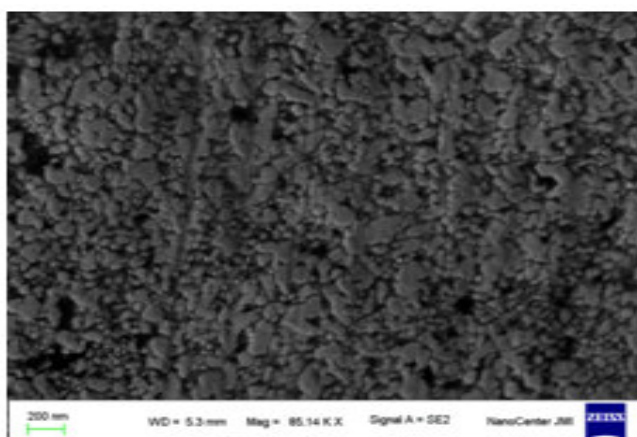


Figure 3
SEM micrograph of AgNPs

TEM analysis

The bioreduced Ag-NPs were elucidated with the help of TEM to determine the shape and average size of Ag-NPs. HRTEM images of Ag-NPs derived from the extract of *C. sempervirens* are shown in Figure 4. TEM images of Ag-NPs at various magnifications confirmed spherical shapes of silver nanoparticles with most clearly apparent average size of 29 nm and approximately the synthesized Ag-NPs are homogeneous in nature. Further analysis of the silver particles by energy dispersive spectroscopy confirmed the presence of the signal characteristic of elemental

silver. The EDS profile shows a strong silver signal along with weak oxygen, chlorine and aluminium peaks, which may have originated from the biomolecules bound to the surface of the silver nanoparticles Figure 5. Figure 6 shows selected area electron diffraction pattern (SAED) of the silver nanoparticles. The silver particles are crystalline, as can be seen from the selected area diffraction pattern recorded from one of the nanoparticles in the aggregate. SAED spots that corresponded to the different crystallographic planes of face-centered cubic (fcc) structure of elemental silver.

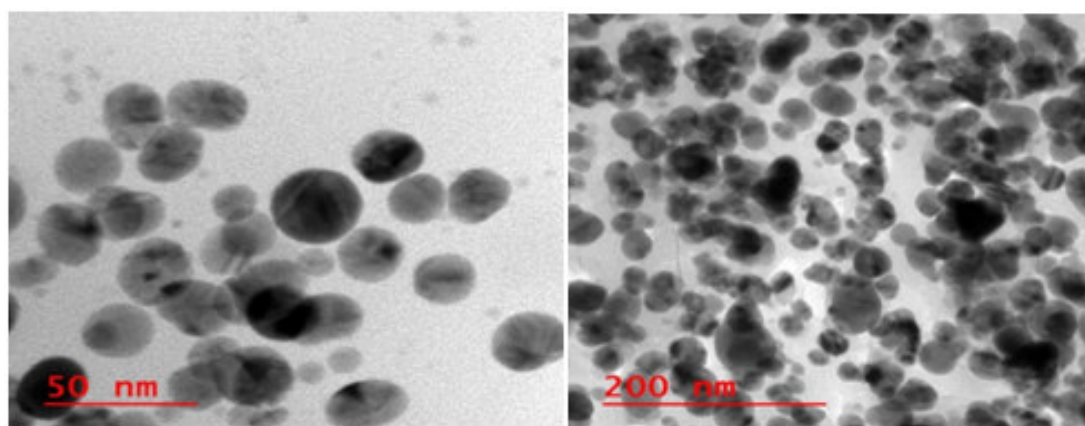


Figure 4
HRTEM images of Ag-NPs of *C. sempervirens*

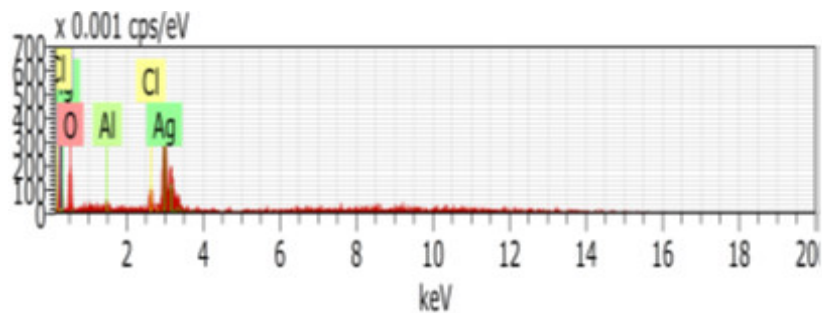


Figure 5
EDX Spectra of Ag-NPs


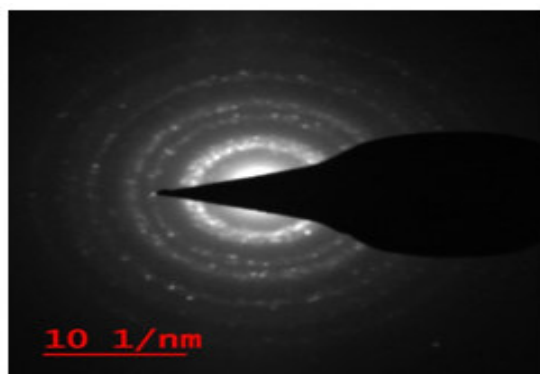


Figure 6
Selected area electron diffraction showing the characteristic crystal planes of elemental silver

Antibacterial activity of Ag-NPs

The antimicrobial activity of biosynthesized silver nanoparticles was examined carried out against both gram positive *B. cereus* and gram negative *K. pneumoniae* bacteria (Figure 7). Biosynthesized silver

nanoparticle showed clear zone of inhibition as indicated in Table-2. Streptomycin 25µg/ml was used as positive Control. Synthesized silver nanoparticles showed significant antibacterial activity against both bacteria.

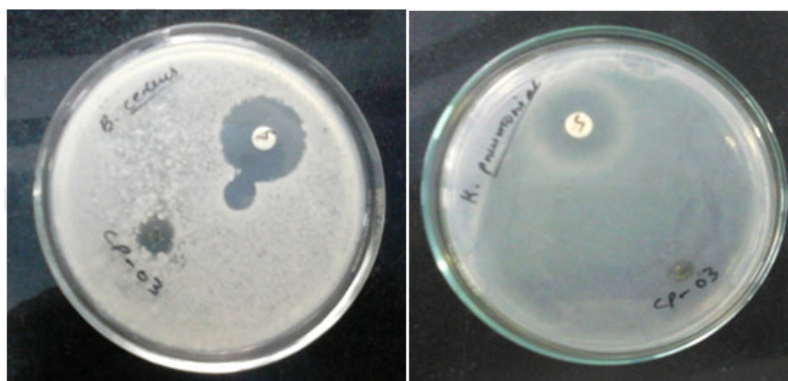

(A)

(B)

Figure 7
Antibacterial studies of synthesized silver nanoparticles of *C. sempervirens*

Table 2
Showing zone of inhibition against bacteria pathogens

| S.NO | Organism | Zone of inhibition (mm) | Positive control (Streptomycin-25µg/ml) |
|------|----------------------|-------------------------|---|
| 1 | <i>B. cereus</i> | 12.3 | 22.6 |
| 2 | <i>K. pneumoniae</i> | 11.6 | 18 |

CONCLUSION

The biogenic silver nanoparticles synthesis from the fruit extract of *C. sempervirens* was studied in this communication. This is a simple, green, ecofriendly and efficient method to synthesize silver nanoparticles at room temperature without using any harmful reducing agents. Silver nanoparticles have been appropriately characterized using UV-vis spectroscopy, XRD, SEM, TEM and EDS analysis. These analysis showed that nanoparticles are crystalline, monodispersed and spherical with average size of 29 nm. The synthesized silver nanoparticles exhibit good significant antimicrobial activity against both bacteria. Therefore, the silver

nanoparticles synthesis by this green method will be priving of potential use in medical applications.

ACKNOWLEDGEMENT

The authors gratefully acknowledge the financial support provided for the research work by the HNB (A Central University) Srinagar Garhwal Uttarakhand Dept. of chemistry, and also JMI New Delhi for technical support.

CONFLICT OF INTEREST

Conflict of interest declared none.

REFERENCES

- Mubayi A, Chatterji S, Rai PM, Watal G. Evidence based green synthesis of nanoparticles. *Adv Mat Lett.* 2012;3(6):519-25.
- El-Nour KM, Eftaiha AA, Al-Warthan A, Ammar RA. Synthesis and applications of silver nanoparticles. *Arabian journal of chemistry.* 2010 Jul 31;3(3):135-40.
- Veerasingam R, Xin TZ, Gunasagaran S, Xiang TF, Yang EF, Jeyakumar N, Dhanaraj SA. Biosynthesis of silver nanoparticles using mangosteen leaf extract and evaluation of their antimicrobial activities. *Journal of Saudi Chemical Society.* 2011 Apr 30;15(2):113-20
- Khatami M, Pourseyedi S. *Phoenix dactylifera* (date palm) pit aqueous extract mediated novel route for synthesis high stable silver nanoparticles with high antifungal and antibacterial activity. *IET Nanobiotechnology.* 2015 Mar 11;9(4):184-90.
- Morones JR, Elechiguerra JL, Camacho A, Holt K, Kouri JB, Ramirez JT, Yacaman MJ. The bactericidal effect of silver nanoparticles. *Nanotechnology.* 2005 Aug 26;16(10):2346.
- Roy S, Das TK. Plant Mediated Green Synthesis of Silver Nanoparticles-A. *Int J Plant Biol Res.* 2015;3(3):1044.
- Bryaskova R, Pencheva D, Nikolov S, Kantardjiev T. Synthesis and comparative study on the antimicrobial activity of hybrid materials based on silver nanoparticles (AgNps) stabilized by polyvinylpyrrolidone (PVP). *Journal of chemical biology.* 2011 Oct 1;4(4):185.
- Franci G, Falanga A, Galdiero S, Palomba L, Rai M, Morelli G, Galdiero M. Silver nanoparticles as potential antibacterial agents. *Molecules.* 2015 May 18;20(5):8856-74.
- Juibari MM, Abbasalizadeh S, Jouzani GS, Noruzi M. Intensified biosynthesis of silver nanoparticles using a native extremophilic *Ureibacillus thermosphaericus* strain. *Materials Letters.* 2011 Mar 31;65(6):1014-7.
- Juibari MM, Yeganeh LP, Abbasalizadeh S, Azarbaijani R, Mousavi SH, Tabatabaei M, Jouzani GS, Salekdeh GH. Investigation of a Hot-Spring Extremophilic *Ureibacillus thermosphaericus* Strain Thermo-BF for Extracellular Biosynthesis of Functionalized Gold Nanoparticles. *BioNanoScience.* 2015 Dec 1;5(4):233-41.
- Anand BG, Thomas CN, Prakash S, Kumar CS. Biosynthesis of silver nano-particles by marine sediment fungi for a dose dependent cytotoxicity against HEp2 cell lines. *Biocatalysis and Agricultural Biotechnology.* 2015 Apr 30;4(2):150-7.
- Moon SA, Salunke BK, Alkotaini B, Sathiyamoorthi E, Kim BS. Biological synthesis of manganese dioxide nanoparticles by *Kalopanax pictus* plant extract. *IET Nanobiotechnology.* 2015 Mar 11;9(4):220-5.
- Ramalingam V, Rajaram R, PremKumar C, Santhanam P, Dhinesh P, Vinothkumar S, Kaleshkumar K. Biosynthesis of silver nanoparticles from deep sea bacterium *Pseudomonas aeruginosa* JQ989348 for antimicrobial, antibiofilm, and cytotoxic activity. *Journal of basic microbiology.* 2014 Sep 1;54(9):928-36.
- de Souza AO, Rodrigues AG. Biosynthesis of silver nanoparticles by fungi. *Fungal Biomolecules: Sources, Applications and Recent Developments.* 2015 Feb 19:115-35.
- Salari Z, Danafar F, Dabaghi S, Ataei SA. Sustainable synthesis of silver nanoparticles using macroalgae *Spirogyra varians* and analysis of their antibacterial activity. *Journal of Saudi Chemical Society.* 2016 Jul 31;20(4):459-64.
- Sinha SN, Paul D, Halder N, Sengupta D, Patra SK. Green synthesis of silver nanoparticles using fresh water green alga *Pithophora oedogonia* (Mont.) Wittrock and evaluation of their antibacterial activity. *Applied Nanoscience.* 2015 Aug 1;5(6):703-9.
- Khatami M, Pourseyedi S, Khatami M, Hamidi H, Zaeifi M, Soltani L. Synthesis of silver nanoparticles using seed exudates of *Sinapis arvensis* as a novel bioresource, and evaluation of their antifungal activity. *Bioresources and Bioprocessing.* 2015 Apr 25;2(1):19.
- Mittal AK, Bhaumik J, Kumar S, Banerjee UC. Biosynthesis of silver nanoparticles: elucidation of prospective mechanism and therapeutic potential. *Journal of colloid and interface science.* 2014 Feb 1;415:39-47.
- Reddy GAK, Joy JM, Mitra T, Shabnam S, Shilpa T. Nanosilver – a review. *International Journal of*

- Advances in Pharmaceutical Sciences. 2012;2(1): 09–15.
20. Srikar SK, Giri DD, Pal DB, Mishra PK, Upadhyay SN. Green Synthesis of Silver Nanoparticles: A Review. Green and Sustainable Chemistry. 2016;6(01):34..
21. Rawat P, Khan MF, Kumar M, Tamarkar AK, Srivastava AK, Arya KR, Maurya R. Constituents from fruits of *Cupressus sempervirens*. Fitoterapia. 2010 Apr 30;81(3):162-6.
22. Krishnaraj C, Jagan EG, Rajasekar S, Selvakumar P, Kalaichelvan PT, Mohan N. Synthesis of silver nanoparticles using *Acalypha indica* leaf extracts and its antibacterial activity against water borne pathogens. Colloids and Surfaces B: Biointerfaces. 2010 Mar 1;76(1):50-6.

Reviewers of this article

Dr. Arun Sharma, Ph.D.

HOD, Chemistry Department,
MITS, Jadan, Pali, 306401,
Rajasthan, India



Asst. Prof. Dr. Sujata Bhattacharya

Assistant Professor, School of Biological
and Environmental Sciences, Shoolini
University, Solan (HP)-173212, India



Prof. Dr. K. Suriaprabha

Asst. Editor, International Journal
of Pharma and Bio sciences.



Prof. P. Muthuprasanna

Managing Editor, International
Journal of Pharma and Bio sciences.

We sincerely thank the above reviewers for peer reviewing the manuscript