



ANTIMICROBIAL AND CYTOTOXIC ACTIVITY OF BIOSYNTHEZED GOLD NANOPARTICLES

S. LOKINA*¹ AND V. NARAYANAN²

¹Department of Chemistry, Rajalakshmi Engineering College, Thandalam, Chennai – 602105, Tamil nadu.

²Department of Inorganic Chemistry, University of Madras, Guindy Maraimalai Campus, Chennai - 600 025, Tamil nadu

ABSTRACT

We present a simple and eco-friendly biosynthesis of gold nanoparticles (AuNPs) using naturally available *Malus domestica* fruit extract as a reducing, capping and stabilizing agent. The reaction process was simple and safe for the formation of highly stable AuNPs at room temperature by using the fruit extract. The surface plasmon resonance (SPR) band in UV-vis spectrum showed the reduction of auric acid to gold nanoparticles at 533 nm. The morphology of the nanoparticles was determined from high resolution transmission electron microscopy (HRTEM), selected area electron diffraction (SAED) and X-ray diffraction (XRD). The HRTEM images showed the mixture of spherical and triangular shapes of biosynthesized AuNPs having size ranging between 5 and 20 nm. Thermogravimetric analysis (TGA) was employed to determine the thermal stability of the AuNPs. They were also characterized by Fluorescence, Raman and Infrared (IR) spectroscopy. The biosynthesized AuNPs showed excellent antibacterial and anticancer activity. The gold nanoparticle synthesized using apple extract showed higher activity against *Aspergillus flavus* (MIC: 0.31 mg/mL) followed by, *Staphylococcus aureus* (MIC: 0.34 mg/mL), *Salmonella typhi* (MIC: 0.63 mg/mL) and *Candida albicans*. Very low activity was found against *Vibrio cholerae* (MIC: 2.50 mg/mL). MTT assay was used to determine the cytotoxicity of biosynthesized gold nanoparticles on HeLa cancer cells.

KEYWORDS: Gold nanoparticles, *Malus domestica*, Green synthesis, Antimicrobial activity, Cytotoxicity



S. LOKINA*

Department of Chemistry, Rajalakshmi Engineering College, Thandalam, Chennai – 602105, Tamil nadu.

Received on: 09.11.2016

Revised and Accepted on : 22-03-2017

DOI: <http://dx.doi.org/10.22376/ijpbs.2017.8.2.p203-213>

INTRODUCTION

A number of physical and chemical processes were developed for the synthesis of metal nanoparticles considering their applications in various fields such as catalysis, medicine, detection etc.^{1,2,3} Recently researchers are attracted by nanoparticles for their unique physical and chemical properties, and showed much interest in the search of benign methods for the development of nanoparticles. The energy efficient, low-cost and eco friendly green method can eliminate the various problems faced by the other other physical and chemical methods. Various plant groups from algae to angiosperms possess different phyto-chemicals. There are several reports on the use of, *Basella alba*, *Helianthus annuus*, *Saccharum officinarum*, *Sorghum bicolor*, *Zea mays*, *Medicago sativa* (Alfa alfa), *Aloe vera*, *Capsicum annum*, *Azadirachta indica* (Neem), *Emblica officinalis* (Amla), *Magnolia kobus*, *Coriandrum* sp., *Geranium* sp., for the synthesis of various metal nanoparticles.^{4,5,6} *Malus domestica* belongs to Rosaceae family, is commonly known as apple, the fruit extract of it is a rich source of highly potent antioxidants and is widely used in several traditional medicinal systems for the treatment of cancer and other diseases. Apple extract is primarily composed of a variety of phenolic phytochemicals. such as quercetin, catechin, phloridzin and chlorogenic acid. The antioxidant activity of phenolic compounds play a vital role in absorbing and neutralizing free radicals, quenching singlet and triplet oxygen, or decomposing peroxides. Epicatechin is a naturally occurring phenolic compound in apple with antioxidant properties. Antioxidants are substances which can offer resistance against oxidative stress by scavenging the free radicals. The biocompatibility and non-toxic property of biosynthesized gold nanoparticles have shown their major role of applications in drug delivery, antimicrobial and anticancer activities.⁷ Due to several advantages, the biosynthesized gold nanoparticles has considered as an important biomedical tool for cancer researchers for detecting cancer disease in a very small volume of tissue or cells and interacting with DNA, proteins, enzymes and cell receptors.^{8,9} Gold nanoparticles have been developed for fuel cell applications and they showed their enormous potential as catalysts in a number of chemical reactions.¹⁰ Gold nanoparticles, as colorimetric sensors, can identify if foods are suitable for consumption. They are designed for use as conductors from printable inks to electronic chips.¹¹ The effect of antimicrobial activity of the biosynthesized gold nanoparticles was investigated using various microorganisms such as *Staphylococcus aureus* (SA), *Staphylococcus typhi* (ST), *Vibrio cholerae* (VC), *Candida albicans* (CA) and *Aspergillus flavus* (AF). The Minimum inhibitory concentration (MIC) was determined by Resazurin microtitre assay (REMA).¹² The cytotoxic effect of gold nanoparticles was studied in HeLa cell lines.¹³ In the present study, we have explored an inventive contribution for the synthesis of gold nanoparticles using apple extract. The procedure for the development of stable gold nanoparticles is simple and viable. The biosynthesized gold nanoparticles were characterized by various methods, such as UV-Vis, IR, Fluorescence,

Raman spectroscopy, TGA, HRTEM, XRD and SAED. The biosynthesized gold nanoparticles showed excellent antimicrobial activity towards various bacteria and fungus. They showed an excellent efficacy towards HeLa cancer cell (cervical cancer, caused by Human Papilloma Virus) lines at different concentrations using MTT assay method.

MATERIALS AND METHODS

Materials

Apple fruits were collected from the local market which was used for the synthesis of gold nanoparticles. The chloroauric acid ($\text{HAuCl}_4 \cdot 3\text{H}_2\text{O}$) (99.9%) was purchased from Sigma Aldrich India Minimal Essential Media supplemented (MEM) was purchased from Hi Media Laboratories and Fetal bovine serum (FBS) was purchased from Cistron laboratories, Dubai. Dimethyl sulfoxide (DMSO), Methylthiazolyldiphenyl- tetrazolium bromide (MTT) and Trypsin were purchased from Sisco Research Laboratory chemicals, Mumbai. The bacterial cultures of *Staphylococcus aureus* (ATCC 25175), *Salmonella typhi* (ATCC 14028), *Vibrio cholerae* (ATCC 14035), *Candida albicans* (ATCC 10231), *Aspergillus flavus* (ATCC 10124) were obtained from National Center for Cell Science (NCCS), Pune. Resazurin (redox) dye was obtained from Sigma Aldrich chemicals., India. A HeLa cell line for cytotoxic study was obtained from King Institute, Guindy, Chennai.

Synthesis of gold nanoparticles

An apple was thoroughly washed, crushed and filtered through Whatman No.1 filter paper. The aqueous solution of 0.01M HAuCl_4 was prepared and added to the aqueous solution of apple extract. The color change in the solution indicated the reduction of auric chloride to gold nanoparticles. To avoid the agglomeration of biosynthesized stable gold nanoparticles lyophilisation process was used.

Characterization of gold nanoparticles

Spectral analysis of nanoparticle formation was observed by UV-Vis spectroscopy using a Perkin-Elmer UV-Visible spectrophotometer of model 1800. Bruker FTIR spectrophotometer was employed for analyzing the functional groups present in biosynthesized gold nanoparticles. High resolution transmission electron microscope of model FEI-TECNAL-30 was used for the analysis of size and shape of developed nanoparticles. 3 μL of the sample solution was placed on copper grid making a thin film of sample on the grid for HRTEM measurements. To determine the phase and crystal structure of gold nanoparticles, XRD measurements were done using a model 3000 from Rich Siefert, Germany and was used with $\text{Cu-K}\alpha_1$ radiation using λ value of 1.54056 Å. A model TGA Q50 V20.13 was used to determine the moisture absorption content and degradation temperatures of gold nanoparticles. Cary fluorescence spectrophotometer of model FL1201M002 was employed to carry out fluorescence measurements. The Raman measurements were carried out using BRUKER RFS 27: Stand-alone FT-Raman spectrometer equipped with Nd:YAG 1064 nm as an excitation source.

RESULTS AND DISCUSSION

UV-Vis analysis

Equivalent amounts of the suspension were diluted in a constant volume of distilled water and subsequently analyzed at room temperature. The progress of the reaction between metal ions and the fruit extracts were shown by the colour change from yellow to black (Inset Fig 1). UV-visible spectrum of biosynthesized gold nanoparticles in aqueous solution was recorded at

different reaction times. At the initial stage, no characteristic SPR peak was observed.^{14,15,16} The SPR peak started to appear in the visible range at 533 nm after 12 h of time. (Fig 1). The polyphenols present in the apple fruit extract act as a reducing and stabilizing agent in the synthesis of gold nanoparticles. The UV-Vis spectrum was recorded after 3 months and it showed an absorption peak at the same wavelength at 533 nm to confirm the stability of gold nanoparticles.

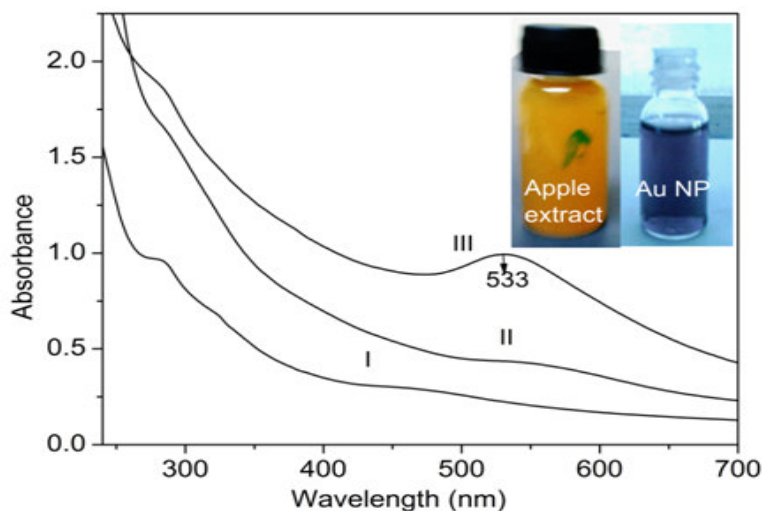


Figure 1

UV- Vis spectra of biosynthesized gold nanoparticles (I) Pure apple extract, Immediately after the addition of HAuCl_4 to apple extract (II) 2 h and (III) 12 h.

Inset Figure Digital photograph of apple fruit extract and gold nanoparticles

FTIR spectroscopy

The FTIR spectrum of gold nanoparticles using apple extract shows absorption bands at 3450, 2904, 2851, 1718, 1632, 1385, 1029 and 637 cm^{-1} (Fig 2). A strong band at 3450 cm^{-1} assigned for broad O-H stretching of water, phenols or alcohols. A peak at 2904 cm^{-1} showed the presence of O-H stretch in carboxylic acid group. The band positioned at 2851 cm^{-1} is due to the presence of aldehyde group. The peak at 1718 cm^{-1} corresponds to C = O stretching vibration for the presence of

carbonyl group. The peak located at 1632 cm^{-1} could be attributed to amide group and 1385 cm^{-1} showed the presence of C-O groups from polyols which act as both reducing and capping agent for the stability of the bio-reduced gold nanoparticles.^{17,18} The peak at 1029 cm^{-1} corresponds to C-OH stretching vibration. It is a well known fact that proteins can bind to gold nanoparticles through free amine groups. The band at 637 cm^{-1} confirmed the presence of alkyl halides.

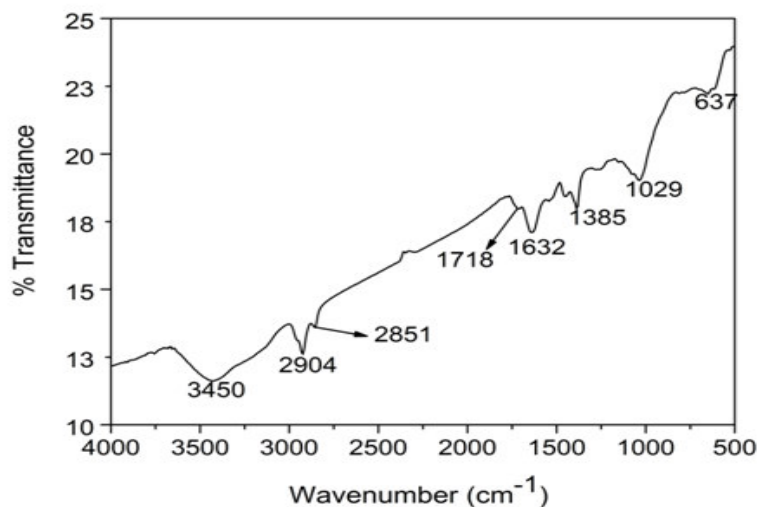


Figure 2

FTIR spectrum of biosynthesized gold nanoparticles

Raman spectroscopic analysis

The Raman spectrum shows bands at 525, 609, 649, 692, 724, 845, 891, 989, 1027, 1079, 1154, 1254, 1313 and 1390 cm^{-1} (Fig 3). The peak at 525 cm^{-1} is due to C-N-C stretching vibration. The peaks at 609, 649 and 692 cm^{-1} assigned to the stretching vibrations of C-S-C. The peak at 724 cm^{-1} is due to the CH_2 rocking vibration mode.¹⁹ The peaks at 1154 cm^{-1} and 1254 cm^{-1} is

assigned to C-C stretching vibration. The peaks at 1254; 845 and 891 cm^{-1} have come from the C-H in plane bending and out of plane wagging, respectively. The band at 989, 1027 and 1079 cm^{-1} is assigned to C-O stretching vibration. The peaks at 1313 and 1390 cm^{-1} are due to asymmetric C=O stretching vibrations of carboxylate group.

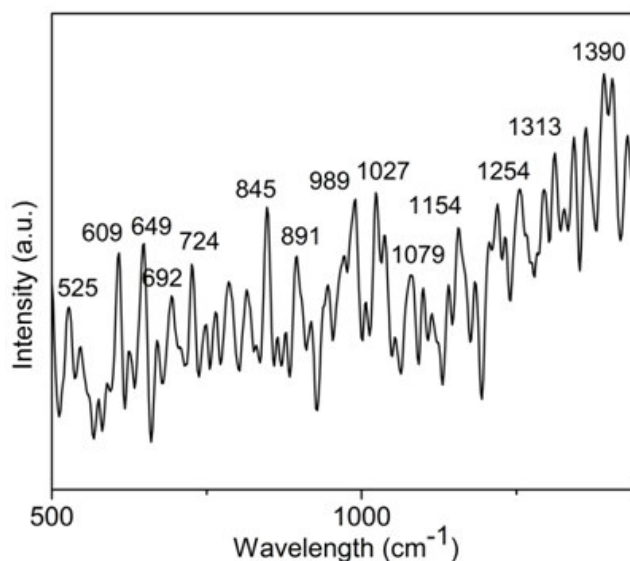


Figure 3
Raman spectrum of biosynthesized gold nanoparticles

Fluorescence spectroscopy analysis

Photoluminescence of apple mediated gold nanoparticles were examined to know its fluorescence property. They were excited at 450 nm and emission of fluorescence was obtained at 546 nm (Fig 4). The origin

of the fluorescence can be attributed to the promotion of d-band electrons of the gold nanoparticles on absorption of the incident photon energy, to higher electronic states in the sp-band.

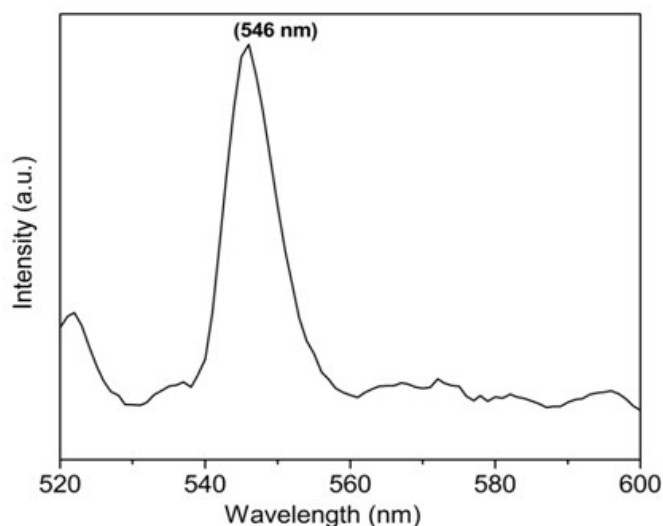


Figure 4
Fluorescence spectrum of biosynthesized gold nanoparticles

TGA

The thermal stability of the biosynthesized gold nanoparticles was recorded by TGA analysis at a heating rate of 20 $^{\circ}\text{C}/\text{min}$ in flowing nitrogen. The thermal decomposition process is represented by TGA curves where the gold nanoparticles were subjected to a heating from 50 to 800 $^{\circ}\text{C}$. In thermogram, it showed multiple falls in weight over the temperature ranges from

50 to 200 $^{\circ}\text{C}$, 200 to 320 $^{\circ}\text{C}$, 320 to 490 $^{\circ}\text{C}$, 490 to 800 $^{\circ}\text{C}$ (Fig 5). The weight loss between 50 to 200 $^{\circ}\text{C}$ was attributed to residual water evaporation, whereas the rest are due to the decomposition of organic contents.²⁰ The residual mass of 41% indicates that high amount of organic contents were present in the biosynthesized gold nanoparticles.

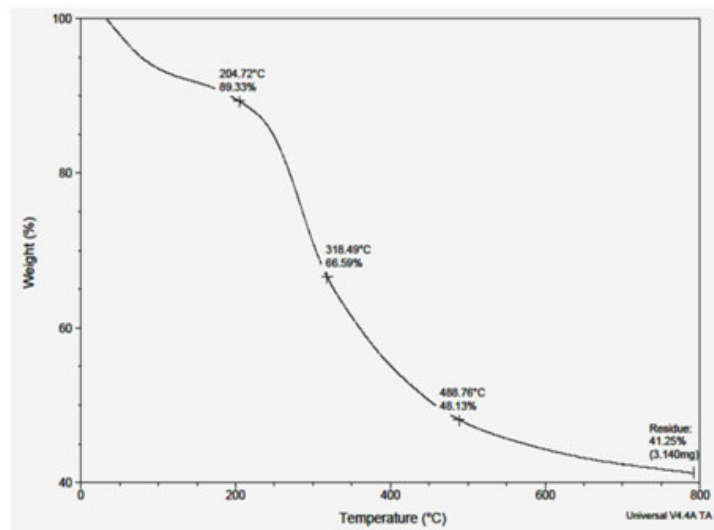


Figure 5
TGA of biosynthesized gold nanoparticles

XRD analysis

The X-ray diffraction (XRD) pattern of the prepared gold nanoparticles is shown in Fig 6. In the XRD pattern of gold nanoparticles, diffraction peaks at 38.0°, 44.3° and 64.3° can be assigned to face-centered cubic (fcc) metallic gold corresponding to the (111), (200) and (220) of the gold crystals. The peaks were well matched with the standard gold particles with JCPDS No-03-065-2870. The interplanar spacing, d values are 2.36, 2.04 and 1.44 Å for (111), (200) and (220) planes

respectively. The results are in good agreement with the reported literature.^{21, 22} The crystallite size of biosynthesized gold nanoparticles was calculated from the width of the XRD peaks, assuming that they are free from non-uniform strains, using the Scherrer formula, $D = 0.94 \lambda / \beta \cos \theta$, where D is the average crystallite domain size perpendicular to the reflecting planes, λ is the X-ray wavelength, β is the full width at half maximum (FWHM), and θ is the diffraction angle.

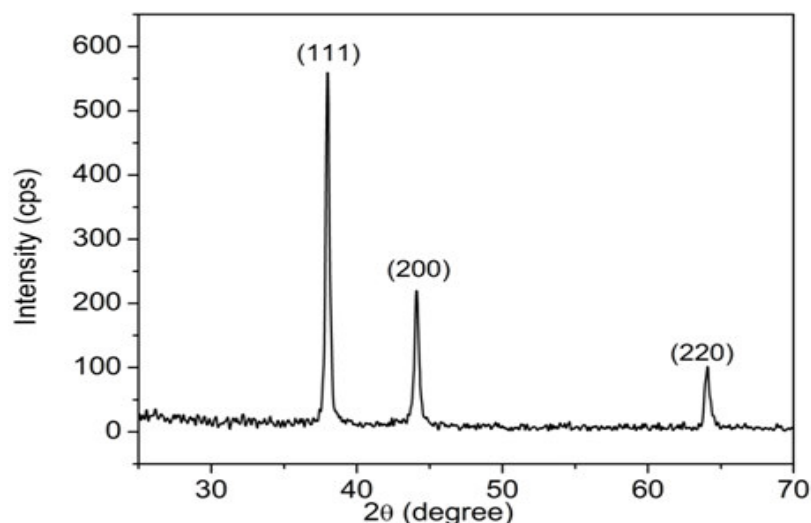


Figure 6
XRD pattern of biosynthesized gold nanoparticles

Morphological analysis

The morphology and size of the biosynthesized gold nanoparticles were examined by FE-SEM (Fig 7a). A typical bright-field HRTEM micrographs showed the mixture of nanoprisms, nanorods and nanospheres of biosynthesized gold nanoparticles (Fig 7b).^{23,24,25} These images suggest that the nanoparticles are polydisperse

and are mostly spherical in shape. It is evident that there is variation in particle sizes and the average size estimated was 5 nm gold nanoparticles (Fig 7c). The spot in SAED pattern reveals that the biosynthesized gold nanoparticles are crystalline in nature (Fig 7d). These rings can be attributed to the diffraction from the (1 1 1), (2 0 0) and (2 2 0) planes of fcc gold.^{26, 27}

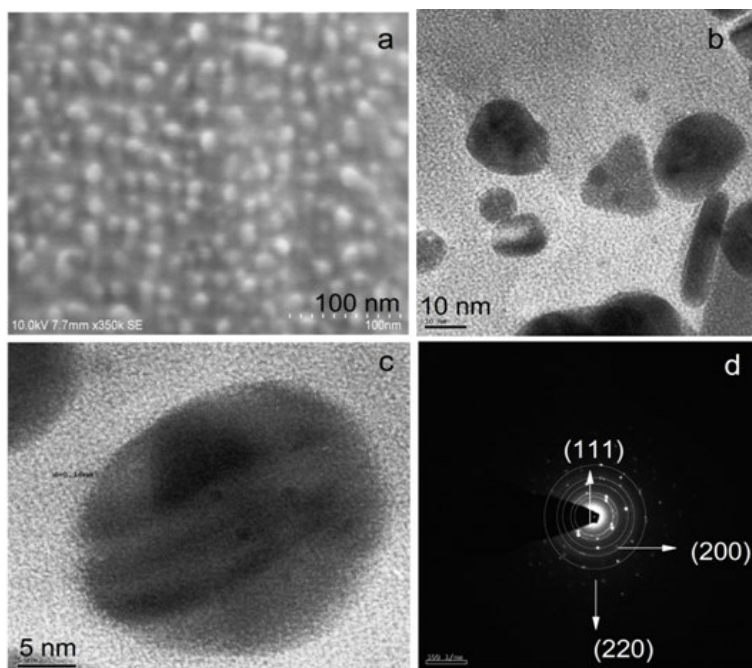


Figure 7

(a) FESEM image and HRTEM images of biosynthesized gold nanoparticles at (b) 10 nm scale and (c) 5 nm scale, (d) SAED pattern showing the characteristic crystal planes of elemental gold

Antimicrobial activity of gold nanoparticles synthesized by using apple extract

Microorganisms and culture medium

All the microorganisms were incubated at 37 °C for 24 h in nutrient broth. The fungus *C. albicans* was incubated in Sabouraud dextrose broth at 37°C for 48 h. The culture suspensions were prepared and adjusted by comparing against 0.4–0.5 Mc Farland turbidity standard tubes. 20 mL of Sabouraud dextrose and Nutrient agar (20 mL) were poured into each sterilized petri dish with 10 mm×100 mm diameter. Then they were allowed to solidify and the bacterial culture and *C. albicans* were swabbed in nutrient agar plates and Sabouraud dextrose plates respectively.²⁸ The gold nanoparticles were dispersed in dimethyl sulfoxide (DMSO) to a final concentration of 100 µg/mL and sterilized by filtration through a 0.22 µm membrane filter for the investigation of the antibacterial and antifungal activity. Each sample was directly filled into the agar plates wells.^{29,30} Plates swabbed with the bacteria culture and the fungus were incubated at 37 °C for 24 h and 37 °C for 48 h respectively. Inhibition zones formed on the medium were measured at the end of the incubation period. The inhibition zones were compared with those of reference discs and inhibitory activity of DMSO was also tested.³¹ Reference values used from reference disc as a control were Tetracycline (30 µg) and Ampicillin (10 µg). All studies were done in triplicate. The cup plate method using nutrient agar was employed to test the antimicrobial activity of the gold nanoparticles. The radial growth of the colony was recorded on completion of the incubation of the bactericidal growth and the mean diameter for each at a concentration of 100 µg/mL was recorded. The average percentage inhibition was compared using the Vincent equation: $I = 100(C-T)/C$, where I= percentage inhibition, T= average diameter of the bacterial growth on the tested plates and C=average diameter of the growth on the control plates.³²

Determination of minimum inhibitory concentration (MIC) using Resazurin Microtitre Assay (REMA)

Preparation of Resazurin solution

Isosensitest medium was used to carry out the test to determine the MIC of the gold nanoparticles. The biosynthesized gold nanoparticles showed similar results for most of the tested bacterial strains.^{33,34} The resazurin solution was prepared by dissolving 270 mg in 40 mL of sterile distilled water. A vortex mixer was used to obtain the homogenous solution. The test was carried out in a sterile 96 well plates. Resazurin indicator (10 µL) solution and 3.3 × strength isosensitised broths (30 µL) were added to each well. 5 × 10⁶ cfu/mL of the bacterial suspension was added to each well. The triplicate plates were placed in an incubator for 18–24 h at 37 °C. The colour change from purple to pink or colourless was recorded as positive.

MIC of gold nanoparticles synthesized by using apple extract

The MIC study was conducted to investigate the antimicrobial activity of biosynthesized gold nanoparticles against bacterial strains such as *S. aureus*, *S. typhi*, *V. cholerae* and against the fungus *C. albicans* and *A. flavus*. The colour change from purple to pink or colorless was recorded as positive.³⁵ The MIC value was taken from the lowest concentration and the average of the three values was calculated. Fig 8 compared the MIC of gold nanoparticles against various microorganisms.³⁶ The MIC of the gold nanoparticles synthesized using apple extract was summarized in Table 1. The gold nanoparticle synthesized using apple extract showed higher activity against *A. flavus* (MIC: 0.31 mg/mL) followed by, *S. aureus* (MIC: 0.34 mg/mL), *S. typhi* (MIC: 0.63 mg/mL) and *C. albicans*. Very low activity was found against *V. cholerae* (MIC: 2.50 mg/mL).

Table 1
MIC of biosynthesized gold nanoparticles synthesized using apple extract against microorganisms

S.No	Microorganisms	MIC (mg/mL)
1	<i>C. albican</i>	1.25
2	<i>A. flavus</i>	0.31
3	<i>S. aureus</i>	0.34
4	<i>S. typhi</i>	0.63
5	<i>V. cholerae</i>	2.50

Average of three experiments

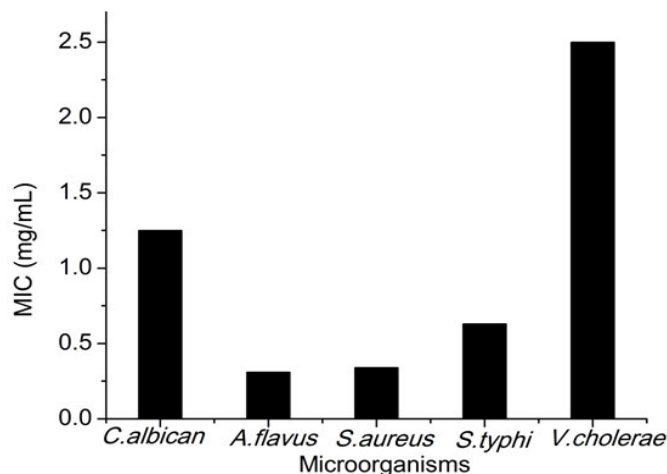



Figure 8

MIC of biosynthesized gold nanoparticles against various microorganisms

Mechanism of antibacterial activity of gold nanoparticle on bacterial cells

The biosynthesized gold nanoparticles easily entered into bacterial cell. They combined with respiratory

enzyme, protease enzyme and DNAs of bacteria. The cell functions of bacteria were deactivated by releasing the gold ion which damaged the cell and lead to the death of bacterial cell (Scheme 1)³⁷.

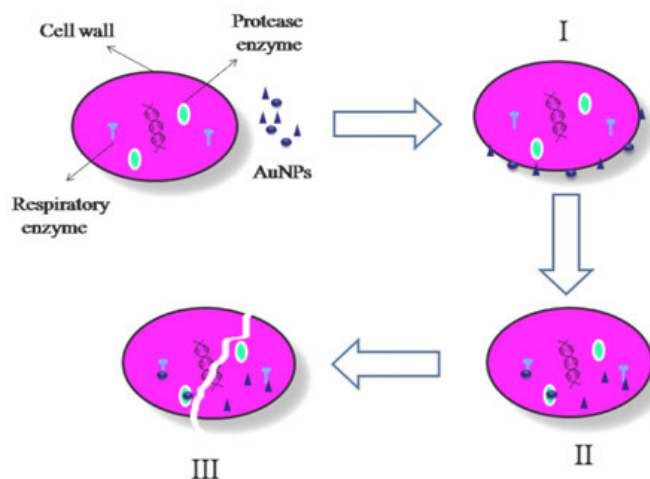

Scheme 1

Mechanism of antimicrobial activity of biosynthesized AuNPs

- (I) Bacterial cells take up biosynthesized AuNPs
- (II) Interaction of AuNPs with respiratory and protease enzyme
- (III) Destruction of bacterial cells by AuNPs

Cytotoxicity of gold nanoparticles against hela cancer cells

Cell culture and medium

HeLa cell lines were maintained in MEM and supplemented with 10% fetal bovine serum (FBS), streptomycin (100 µg/mL) and penicillin (100 µg/mL) in a humidified atmosphere of 50 µg/mL CO₂ at 37 °C.

MTT assay for cytotoxicity (In-vitro)

MTT assay was used to determine the cytotoxicity of biosynthesized gold nanoparticles on HeLa cancer cells.³⁸ Gupta *et al.*, were plated in 1ml of medium in 24-well plates (Costar Corning, Rochester, NY). The cell reaches the confluence after 48 h of incubation. Then

the cells were incubated in the presence of various concentrations of the samples in 0.1% DMSO for 48 h at 37°C. The sample solution was removed and washed with PBS of 200 μ L/well (5 mg/mL) and pH 7.4. Isopropanol /HCl of 0.04 M were added after 4 h of incubation. Viable cells showed their absorbance at 570 nm which was measured with a UV- Spectrophotometer using wells without sample containing cells as blanks. The concentration required for a 50% inhibition of viability (IC_{50}) was determined graphically.³⁹ The effect of the samples on the proliferation of HeLa was expressed as the % cell viability, using the formula, % cell viability = A_{570} of treated cells / A_{570} of control cells \times 100%. The cell viability of HeLa cancer cells was assessed by MTT assay for 48 h after treatment with the gold nanoparticles.⁴⁰ The cytotoxicity results were shown in Table 2 for different concentrations (1000, 500, 250, 125, 62.5, 31.2, 15.6, 7.8 μ g/mL) of gold

nanoparticles. Viable cells were determined by the absorbance at 570 nm. The normal HeLa cells were shown in Fig 9a and the cytotoxicity effect of gold nanoparticles at various concentrations like 1000, 250, 62.5 and 31.2 μ g/mL on HeLa cells were shown in Fig 9b-e. The results revealed that the % cell viability at high dose of 1000 μ g/mL is 8.9. But, when the doses were decreased like 500, 250, 125, 62.5, 31.2, 15.6 and 7.8 μ g/mL, then the percentage of viable cells was increased to 22.3, 35.8, 47.7, 56.7, 64.1, 68.6 and 79.6 respectively. 91.1% of cancer cells were dead at high dose of 1000 μ g/mL. The results of present work demonstrate the IC_{50} of gold nanoparticles as 125 μ g/mL for HeLa cervical cancer cell lines (Fig 10). The experimental results clearly proved the excellent anticancer activity of gold nanoparticles against the HeLa cell line.⁴¹

Table 2
Cell viability of biosynthesized AuNPs on HeLa cell lines

S.No	Concentration (μ g/mL)	Dilutions	Absorbance (O.D)	Cell viability (%)
1	1000.0	Neat	0.06	8.9
2	500.0	1:1	0.15	22.3
3	250.0	1:2	0.24	35.8
4	125.0	1:4	0.32	47.7
5	62.5	1:8	0.38	56.7
6	31.2	1:16	0.43	64.1
7	15.6	1:32	0.46	68.6
8	7.8	1:64	0.53	79.6
9	Cell control	-	0.67	100

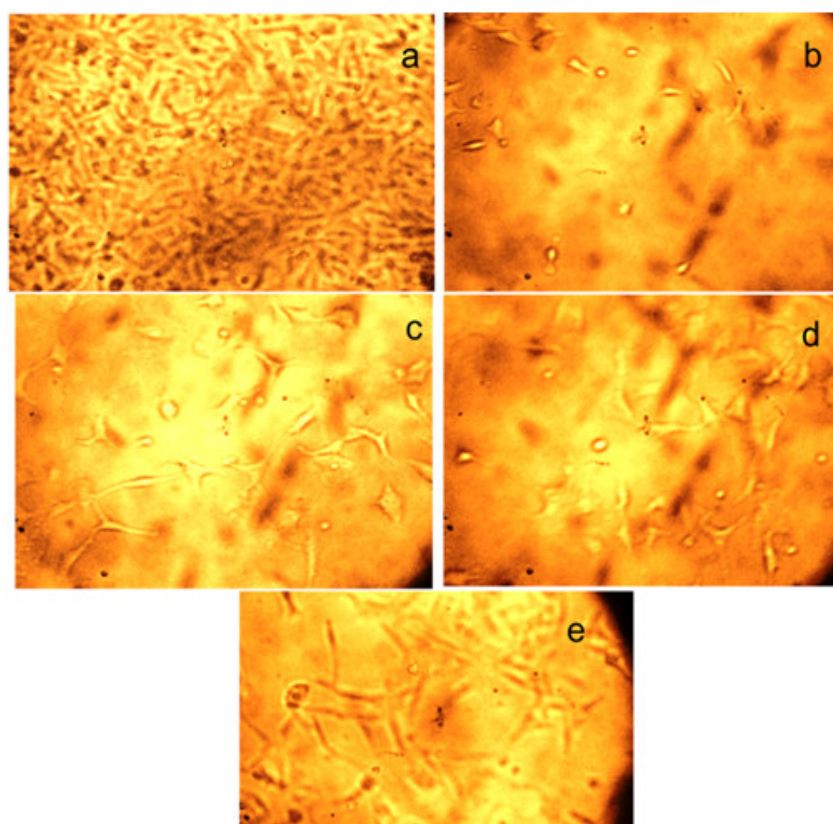


Figure 9

Microscopic images of HeLa cells (a) after 24 h incubation; cells without any treatment (b) at 1000 μ g/mL (b) 250 μ g/mL (c) 62.5 μ g/mL (e) 31.2 μ g/mL of gold nanoparticles synthesized using apple extract.

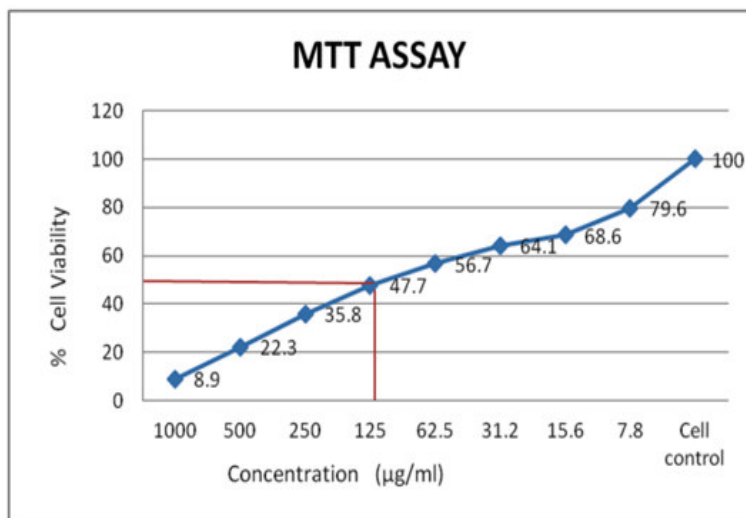


Figure 10
Cell viability of the biosynthesized gold nanoparticles at different concentration.

CONCLUSION

This simple and eco friendly method for the synthesis of gold nanoparticles played an important tool in the area of nanotechnology and green synthesis. In this work, apple fruit extract was prepared and successfully employed for the development of gold nanoparticles with spherical and triangular shapes. The polyphenols and flavanoids present in apple extract played a vital role in the reduction of auric acid and stabilization of gold nanoparticles. XRD study showed the face-centered cubic lattice of gold nanoparticles. The HRTEM images confirmed the crystalline nature of biosynthesized gold nanoparticles. SAED pattern showed the characteristic crystal plane of elemental gold. They showed their

excellent potential in antimicrobial activity towards various microorganisms. The gold nanoparticles synthesized using apple extract showed significant cytotoxic effects against HeLa cancer cell lines.

ACKNOWLEDGMENT

We gratefully acknowledge National Centre for Nanoscience and Nanotechnology, University of Madras for FESEM, HRTEM and SAED analysis.

CONFLICT OF INTEREST

Conflict of interest declared none.

REFERENCES

- Hickey N, Arneodo Larochette P, Gentilini C, Sordelli L, Olivi L, Polizzi S, Montini T, Fornasiero P, Pasquato L, Graziani M. Monolayer protected gold nanoparticles on ceria for an efficient CO oxidation catalyst. *Chemistry of materials*. 2007 Feb 20;19(4):650-1.
- Sperling RA, Gil PR, Zhang F, Zanella M, Parak WJ. Biological applications of gold nanoparticles. *Chemical Society Reviews*. 2008;37(9):1896-908.
- Hu J, Wang Z, Li J. Gold nanoparticles with special shapes: controlled synthesis, surface-enhanced Raman scattering, and the application in biodetection. *Sensors*. 2007 Dec 14;7(12):3299-311.
- Choi SM, Seo MH, Kim HJ, Kim WB. Synthesis and characterization of graphene-supported metal nanoparticles by impregnation method with heat treatment in H₂ atmosphere. *Synthetic Metals*. 2011 Dec 31;161(21):2405-11.
- Gardea-Torresdey JL, Parsons JG, Gomez E, Peralta-Videa J, Troiani HE, Santiago P, Yacaman MJ. Formation and growth of Au nanoparticles inside live alfalfa plants. *Nano letters*. 2002 Apr 10;2(4):397-401.
- Gardea-Torresdey JL, Gomez E, Peralta-Videa JR, Parsons JG, Troiani H, Jose-Yacaman M. Alfalfa sprouts: a natural source for the synthesis of silver nanoparticles. *Langmuir*. 2003 Feb 18;19(4):1357-61.
- Zhang H, Hu N. Assembly of myoglobin layer-by-layer films with poly (propyleneimine) dendrimer-stabilized gold nanoparticles and its application in electrochemical biosensing. *Biosensors and Bioelectronics*. 2007 Oct 31;23(3):393-9.
- Patra CR, Bhattacharya R, Mukhopadhyay D, Mukherjee P. Application of gold nanoparticles for targeted therapy in cancer. *Journal of Biomedical Nanotechnology*. 2008 Jun 1;4(2):99-132.
- Marchal F, Pic E, Pons T, Dubertret B, Bolotine L, Guillemin F. [Quantum dots in oncological surgery: the future for surgical margin status]. *Bulletin du cancer*. 2008 Dec;95(12):1149-53.
- Thompson DT. Using gold nanoparticles for catalysis. *Nano Today*. 2007 Aug 31;2(4):40-3.
- Huang D, Liao F, Molesa S, Redinger D, Subramanian V. *Journal of the Electrochem Soc* 2003; 150: G412-417.
- Lokina S, Stephen A, Kaviyaran V, Arulvasu C, Narayanan V. Cytotoxicity and antimicrobial

- activities of green synthesized silver nanoparticles. European journal of medicinal chemistry. 2014 Apr 9;76:256-63.
13. Mosmann T. Rapid colorimetric assay for cellular growth and survival: application to proliferation and cytotoxicity assays. Journal of immunological methods. 1983 Dec 16;65(1-2):55-63.
 14. Noginov MA, Zhu G, Bahoura M, Adegoke J, Small C, Ritzo BA, Drachev VP, Shalaev VM. The effect of gain and absorption on surface plasmons in metal nanoparticles. Applied Physics B. 2007 Feb 1;86(3):455-60.
 15. Kasthuri J, Veerapandian S, Rajendiran N. Biological synthesis of silver and gold nanoparticles using apiin as reducing agent. Colloids and Surfaces B: Biointerfaces. 2009 Jan 1;68(1):55-60.
 16. Nagaraj B, Krishnamurthy NB, Liny P, Divya TK and Dinesh R. Biosynthesis of gold nanoparticles of *Ixora Coccinea* flower extract and their antimicrobial activities. International Journal of Pharma and Bio Sciences. 2011; 2, 557- 565.
 17. Shahverdi AR, Fakhimi A, Shahverdi HR, Minaian S. Synthesis and effect of silver nanoparticles on the antibacterial activity of different antibiotics against *Staphylococcus aureus* and *Escherichia coli*. Nanomedicine: Nanotechnology, Biology and Medicine. 2007 Jun 30;3(2):168-71.
 18. Lokina S, Narayanan V. Antimicrobial and anticancer activity of gold nanoparticles synthesized from grapes fruit extract. Chemical Science Transactions. 2013;2(S1):S105-10.
 19. Cooney RP, Barraclough CG, Healy TW. Nonionic surfactant structure in the liquid and micelle states: a Raman spectroscopic study. The Journal of Physical Chemistry. 1983 May;87(11):1868-73.
 20. Navaladian S, Viswanathan B, Viswanath RP, Varadarajan TK. Thermal decomposition as route for silver nanoparticles. Nanoscale research letters. 2007 Jan 1;2(1):44-8.
 21. Dwivedi AD, Gopal K. Biosynthesis of silver and gold nanoparticles using *Chenopodium album* leaf extract. Colloids and Surfaces A: Physicochemical and Engineering Aspects. 2010 Oct 20;369(1):27-33.
 22. Kannan P, John SA. Synthesis of mercaptothiadiazole-functionalized gold nanoparticles and their self-assembly on Au substrates. Nanotechnology. 2008 Feb 1;19(8):085602.
 23. Philip D, Unni C, Aromal SA, Vidhu VK. Murraya koenigii leaf-assisted rapid green synthesis of silver and gold nanoparticles. Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy. 2011 Feb 28;78(2):899-904.
 24. Best RB, Brockwell DJ, Toca-Herrera JL, Blake AW, Smith DA, Radford SE, Clarke J. Force mode atomic force microscopy as a tool for protein folding studies. Analytica Chimica Acta. 2003 Mar 5;479(1):87-105.
 25. Liny P, Divya TK, Barasa M, Nagaraj B, Krishnamurthy NB, Dinesh R. Preparation of gold nanoparticles from *Helianthus annuus* (sun flower) flowers and evaluation of their antimicrobial activities. International Journal of Pharma and Bio Sciences. 2012;3(1):439-46.
 26. Philip D. Biosynthesis of Au, Ag and Au–Ag nanoparticles using edible mushroom extract. Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy. 2009 Jul 15;73(2):374-81.
 27. Lokina S, Suresh R, Giribabu K, Stephen A, Sundaram RL, Narayanan V. Spectroscopic investigations, antimicrobial, and cytotoxic activity of green synthesized gold nanoparticles. Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy. 2014 Aug 14;129:484-90.
 28. Fayaz AM, Balaji K, Girilal M, Yadav R, Kalaichelvan PT, Venketesan R. Biogenic synthesis of silver nanoparticles and their synergistic effect with antibiotics: a study against gram-positive and gram-negative bacteria. Nanomedicine: Nanotechnology, Biology and Medicine. 2010 Feb 28;6(1):103-9.
 29. Rai M, Yadav A, Gade A. Silver nanoparticles as a new generation of antimicrobials. Biotechnology advances. 2009 Feb 28;27(1):76-83.
 30. Lee D, Cohen RE, Rubner MF. Antibacterial properties of Ag nanoparticle loaded multilayers and formation of magnetically directed antibacterial microparticles. Langmuir. 2005 Oct 11;21(21):9651-9.
 31. Das SK, Das AR, Guha AK. Gold nanoparticles: microbial synthesis and application in water hygiene management. Langmuir. 2009 May 8;25(14):8192-9.
 32. Vincent JM. Distortion of fungal hyphae in the presence of certain inhibitors. Nature. 1947 Jun 21;159(4051):850.
 33. Yu-sen EL, Vidic RD, Stout JE, McCartney CA, Victor LY. Inactivation of *Mycobacterium avium* by copper and silver ions. Water Research. 1998 Jul 31;32(7):1997-2000.
 34. Sheena N, Ajith TA, Mathew A, Janardhanan KK. Antibacterial activity of three macrofungi, *Ganoderma lucidum*, *Navesporus floccosa* and *Phellinus rimosus* occurring in South India. Pharmaceutical biology. 2003 Jan 1;41(8):564-7.
 35. Wiegand I, Hilpert K, Hancock RE. Agar and broth dilution methods to determine the minimal inhibitory concentration (MIC) of antimicrobial substances. Nature protocols. 2008 Jan 1;3(2):163-75.
 36. Owoyele BV, Okoye OC, Dolor RO, Oloruntola OP, Soladoye AO. Analgesic, anti-inflammatory and antipyretic effects of the ethanol extract of *Acalypha wilkesiana* leaves in rats. Nigerian Journal of Physiological Sciences. 2011 Nov 23;26(1).
 37. Gupta A, Mehra P, Dhar SK. Plasmodium falciparum origin recognition complex subunit 5: functional characterization and role in DNA replication foci formation. Molecular microbiology. 2008 Aug 1;69(3):646-65.
 38. Mosmann T. Rapid colorimetric assay for cellular growth and survival: application to proliferation and cytotoxicity assays. Journal of immunological methods. 1983 Dec 16;65(1- 2):55-63.

40. Khan JA, Pillai B, Das TK, Singh Y, Maiti S. Molecular effects of uptake of gold nanoparticles in HeLa cells. *Chembiochem*. 2007 Jul 23;8(11):1237-40.
41. Sukirtha R, Priyanka KM, Antony JJ, Kamalakkannan S, Thangam R, Gunasekaran P, Krishnan M, Achiraman S. Cytotoxic effect of Green synthesized silver nanoparticles using *Melia azedarach* against in vitro HeLa cell lines and lymphoma mice model. *Process Biochemistry*. 2012 Feb 29;47(2):273-9.
42. Brandão GC, Kroon EG, dos Santos JR, Stehmann JR, Lombardi JA, de Oliveira AB. Antiviral activity of plants occurring in the state of Minas Gerais (Brazil): part III. *Journal of Chemical and Pharmaceutical Research*. 2011 Aug 12:223-36.

Reviewers of this article

Dr. R. Jayasree

HOD, Department of Biotechnology,
Rajalakshmi Engineering College,
Thandalam, Chennai - 602105,
India



Asst.Prof.Dr. Sujata Bhattacharya

Assistant Professor, School of Biological
and Environmental Sciences, Shoolini
University, Solan (HP)-173212, India



Prof.Dr.K.Suriaprabha

Asst. Editor , International Journal
of Pharma and Bio sciences.



Prof.P.Muthuprasanna

Managing Editor , International
Journal of Pharma and Bio sciences.

We sincerely thank the above reviewers for peer reviewing the manuscript